

# Non-Drude universal scaling laws for the optical response of local Fermi liquids

Christophe Berthod,<sup>1</sup> Jernej Mravlje,<sup>2,3,4</sup> Xiaoyu Deng,<sup>5</sup> Rok Žitko,<sup>4</sup> Dirk van der Marel,<sup>1</sup> and Antoine Georges<sup>3,2,1</sup>

<sup>1</sup>*Département de Physique de la Matière Condensée, Université de Genève,  
24 quai Ernest-Ansermet, 1211 Genève 4, Switzerland*

<sup>2</sup>*Collège de France, 11 place Marcelin Berthelot, 75005 Paris, France*

<sup>3</sup>*Centre de Physique Théorique, École Polytechnique, CNRS, 91128 Palaiseau, France*

<sup>4</sup>*Jožef Stefan Institute, Jamova 39, Ljubljana, Slovenia*

<sup>5</sup>*Department of Physics, Rutgers University, Piscataway, NJ 08854, USA*

(Dated: December 26, 2012)

We investigate the frequency and temperature dependence of the low-energy electron dynamics in a Landau Fermi-liquid with a local self-energy. We show that the frequency and temperature dependence of the optical conductivity obeys a universal scaling form, for which an explicit analytical expression is obtained. For the optical conductivity and the associated memory function, we obtain a number of surprising features which differ qualitatively from the Drude-model and are universal characteristics of a Fermi liquid. Different physical regimes of scaling are identified, with marked non-Drude features in the regime where  $\hbar\omega \sim k_B T$ . These analytical results for the optical conductivity are compared to numerical calculations for the doped Hubbard model within dynamical mean-field theory. For the ‘universal’ low energy electrodynamics, we obtain perfect agreement between numerical calculations and analytical scaling laws. Both results show that the optical conductivity displays a non-Drude ‘foot’, which could be easily mistaken as a signature of breakdown of the Fermi liquid, while it actually is a striking signature of its applicability. The aforementioned scaling laws provide a quantitative tool for the experimental identification and analysis of the Fermi-liquid state using optical spectroscopy, and a powerful method for the identification of alternative states of matter, when applicable.

PACS numbers: 78.20.Bh, 78.47.db, 72.15.Lh

## I. INTRODUCTION

A century after its elaboration, the Drude formula is still commonly used to analyze the electrodynamic response of metals.<sup>1,2</sup> However, the conceptual basis underlying Drude’s phenomenological description has been entirely changed by the modern quantum theory of the solid-state. The key point is the emergence of long-lived quasiparticle excitations at low energy and low temperature, which are the actual charge carriers in good metals. Understanding the emergence of quasiparticles from a correlated liquid of interacting electrons is the great achievement of Landau’s Fermi liquid (FL) theory,<sup>3</sup> which is precisely half as old as the Drude theory. In FL theory, the existence of long-lived quasiparticles is due to the vanishing of their scattering rate as the Fermi surface is approached, because of phase-space constraints and the Pauli principle. For quasiparticles to be well-defined, however, they must have a relaxation rate smaller than their energy (and hence than the available thermal excitation energy  $\sim k_B T$ ), a condition which is met at low temperature close to the Fermi surface of simple metals.

When exciting carriers at a low frequency  $\omega$ , one induces intra-band transitions of energy  $\hbar\omega$  between states within windows of order  $k_B T$ , thus probing the relaxation rate up to energies typically  $\hbar\omega + k_B T$ . A Drude-like response is expected if the relaxation rate does not vary appreciably over this energy range. For Landau quasiparticles in a FL, the relaxation rate increases quadratically with increasing energy and temperature. The conditions for a Drude response are therefore met if  $\hbar\omega \ll k_B T$ , but deviations are expected if  $\hbar\omega \gtrsim k_B T$ . Deviations from a pure Drude behavior are actu-

ally common in metals, and this is often somewhat loosely interpreted as a violation of Fermi-liquid behavior. However, in order to distinguish non-Drude features which are consistent with—or even signatures of—FL behavior, from those which indicate a genuine breakdown of FL theory, one needs to understand the response of Landau quasiparticles to electromagnetic waves. This is a difficult task in general, which has regained interest recently,<sup>4,5</sup> along with the development of low-frequency spectrometers.<sup>6,7</sup>

In this article, we address this problem in the context of local Fermi liquids. By ‘local’, we mean that the scattering rate, and more generally the single-particle self-energy, is independent of momentum. From a theory viewpoint, local FLs are realized e.g. in the Dynamical Mean Field Theory (DMFT) of strongly correlated electron models. The success of this approach in practice also demonstrates that a weak momentum-dependence is a reasonable approximation for a wide class of correlated electron materials, at least in some range of composition, temperature, etc..., when spatial correlations are short-ranged.

The considerable simplification resulting from locality allows us to derive here analytically a universal scaling form of the optical conductivity in the FL regime. We show that a Drude-like behavior is indeed recovered in the regime  $\hbar\omega \ll k_B T$ . In contrast, clear departure from Drude behavior is found at higher frequency  $\hbar\omega \sim k_B T$  when the frequency dependence of the scattering rate becomes important. Characteristic non-Drude signatures of FL behavior in the optical conductivity are identified in this regime.

We also perform DMFT calculations of the optical conductivity for a microscopic model of a hole-doped Mott insulator. We show that the results accurately obey the FL scaling ex-

pressions, and that characteristic non-Drude features of the DMFT optical conductivity in the thermal regime  $\hbar\omega \sim k_B T$  are explained by the FL scaling analysis. The model calculation also allows to clearly identify the limitations and range of applicability of universal FL behavior.

Finally, we discuss the conditions for a possible experimental observation of the FL universal scaling laws and FL signatures in optical measurements.

The paper is organized as follows. Section II reviews the Drude theory and its generalizations. In Sec. III, we give the general formula for the optical conductivity of a system with a local self-energy. We then introduce the low-energy expression of the self-energy in a local FL, derive analytically a universal scaling expression for the optical conductivity, and discuss the different regimes of physical relevance. Section IV presents a comparison of the FL scaling laws with DMFT calculations. In Sec. V, we address issues related to the experimental observation of FL scaling laws in the optical conductivity, and discuss in more details the case of  $\text{UPd}_2\text{Al}_3$ . Our conclusions are given in Sec. VI, and a series of appendices collect additional material.

## II. PRELIMINARIES – DRUDE THEORY AND BEYOND

In the Drude theory of conduction in metals, a single frequency-independent time  $\tau_D$  governs the relaxation of the current. The assumption is that the current decays exponentially once the electric field has been turned off. The classical equation of motion then leads to the dc conductivity  $\sigma_{\text{dc}} = ne^2\tau_D/m$ , with  $n$  the carrier density and  $m$  the carrier mass. In the presence of an oscillating electric field, the complex frequency-dependent conductivity  $\sigma(\omega) = \sigma_1(\omega) + i\sigma_2(\omega)$  reads:

$$\sigma(\omega) = \frac{ne^2}{m} \frac{1}{-i\omega + 1/\tau_D} = \frac{\sigma_{\text{dc}}}{1 - i\omega\tau_D}. \quad (1)$$

In many materials however, especially those with strong electron correlations, a single frequency-independent relaxation time does not provide an accurate description of the experimental data.<sup>8</sup> In order to describe the full frequency-dependence of the conductivity, it is convenient to introduce<sup>9</sup> a memory function  $M(\omega)$  such that:

$$\sigma(\omega) = \frac{i\epsilon_0\omega_p^2}{\omega + M(\omega)}. \quad (2)$$

In this expression, we define the plasma frequency from the sum-rule over the whole frequency range:

$$\epsilon_0\omega_p^2 \equiv \frac{2}{\pi} \int_0^\infty d\omega \sigma_1(\omega). \quad (3)$$

The complex function  $M(\omega) = M_1(\omega) + iM_2(\omega)$  plays the role of a self-energy for the optical response. The definition (3) of  $\omega_p^2$  ensures that  $\omega$  dominates over  $M(\omega)$  in

the expression of  $\sigma(\omega)$  at large frequencies. Indeed, the Kramers-Kronig relations:

$$\{\sigma_1(\omega), \sigma_2(\omega)\} = \frac{1}{\pi} \int_{-\infty}^\infty d\Omega \frac{\{-\sigma_2(\Omega), \sigma_1(\Omega)\}}{\omega - \Omega} \quad (4)$$

imply that  $\sigma_2(\omega \sim \infty) \sim 2 \int_0^\infty d\Omega \sigma_1(\Omega)/(\pi\omega)$ .

Expression (2) can be cast in a form which is formally analogous to the Drude expression (“generalized Drude model”):

$$\sigma(\omega) = \epsilon_0\omega_p^2 \frac{\mathcal{D}(\omega)}{-i\omega + 1/\tau_{\text{opt}}(\omega)} \quad (5)$$

with:

$$\mathcal{D}(\omega) = \left[1 + \frac{M_1(\omega)}{\omega}\right]^{-1}, \quad \frac{1}{\tau_{\text{opt}}(\omega)} = \mathcal{D}(\omega)M_2(\omega). \quad (6)$$

Note that the complex conductivity obeys  $\sigma^*(\omega) = \sigma(-\omega)$  under complex conjugation, so that  $\sigma_1$ ,  $M_2$ ,  $\mathcal{D}$  (resp.  $\sigma_2$ ,  $M_1$ ) are even (resp. odd) functions of frequency.  $\mathcal{D}(\omega)$  is often denoted  $m/m^*(\omega)$ , hence defining an optical effective mass, and  $\tau_{\text{opt}}(\omega)$  is often written as  $\tau^*(\omega)$ . At low frequency,  $\mathcal{D}(\omega \rightarrow 0) = (1 + \partial_\omega M_1|_{\omega=0})^{-1}$  renormalizes the bare plasma frequency and the spectral weight of the Drude peak. In many cases, the frequency-dependence of the optical scattering rate  $1/\tau_{\text{opt}}(\omega)$  at low frequency is mainly determined by  $M_2(\omega)$ , with  $\mathcal{D}(\omega)$  having a milder frequency dependence (see below).

When analyzing experimental data, the imaginary part of the memory function which controls the optical scattering rate can for example be determined through:

$$M_2(\omega) = \text{Re} \frac{\epsilon_0\omega_p^2}{\sigma(\omega)}, \quad (7)$$

with the plasma frequency determined by the sum rule (3).

## III. OPTICAL CONDUCTIVITY OF LOCAL FERMI LIQUIDS

We now specialize the discussion to the optical conductivity of *local* Fermi liquids, i.e. systems in which the single-particle self-energy  $\Sigma$  obeys the low-frequency, low temperature behavior of Landau Fermi-liquid theory and, additionally, does not depend on momentum. This is the case, in particular, of strongly correlated electron models and materials treated in the framework of dynamical mean-field theory.<sup>10</sup>

We first recall the simplifications encountered in the Kubo formalism in this context, and the resulting expression of the optical conductivity. We then show that universal scaling laws emerge in the Fermi liquid regime and discuss these laws in the different physical regimes.

### A. General expression of the optical conductivity

When the single-particle self-energy  $\Sigma(\varepsilon)$  has no momentum dependence, the Kubo formalism leads to the following general expression of the optical conductivity:

$$\sigma_1(\omega) = \frac{1}{\omega} \int_{-\infty}^{\infty} d\varepsilon [f(\varepsilon) - f(\varepsilon + \hbar\omega)] \times \pi \int_{-\infty}^{\infty} d\xi \Phi(\xi) A(\xi, \varepsilon) A(\xi, \varepsilon + \hbar\omega) \quad (8a)$$

in which  $f(\varepsilon)$  is the Fermi function, while  $\Phi(\xi)$  and  $A(\xi, \varepsilon)$  are respectively the transport function and the one-particle spectral function, defined in detail below. The derivation of this formula is outlined in Appendix A. The key point is that vertex corrections associated with the current-current correlation function exactly vanish in the case of a local (momentum independent) theory,<sup>11</sup> so that the conductivity can be entirely expressed in terms of the one-particle self-energy.

Expression (8a) of the optical conductivity applies to a single-band system, to which our discussion is limited in this article for simplicity. The entire information about the band dispersion is encoded in the transport function  $\Phi$ , defined by:

$$\Phi(\xi) = \frac{2e^2}{dL^d} \sum_{\mathbf{k}} v_{\mathbf{k}}^2 \delta(\xi - \xi_{\mathbf{k}}). \quad (8b)$$

In this expression,  $L$  is the system size,  $d$  is the dimensionality,  $\xi_{\mathbf{k}} = E_{\mathbf{k}} - \mu$  is the dispersion of the non-interacting Bloch band measured from the chemical potential, and  $v_{\mathbf{k}} = (1/\hbar) \nabla_{\mathbf{k}} E_{\mathbf{k}}$  is the corresponding group velocity. Many-body effects enter through the single-electron spectral function,  $A(\xi, \varepsilon)$  which is related to the self-energy  $\Sigma(\varepsilon) = \Sigma_1(\varepsilon) + i\Sigma_2(\varepsilon)$  by

$$A(\xi, \varepsilon) = \frac{-\Sigma_2(\varepsilon)/\pi}{[\varepsilon - \xi - \Sigma_1(\varepsilon)]^2 + [\Sigma_2(\varepsilon)]^2}. \quad (8c)$$

In all these expressions,  $\varepsilon/\hbar$  designates a frequency, while the momentum dependence of the spectral function stems from  $\xi_{\mathbf{k}}$ .

The transport function  $\Phi(\xi)$  is usually a slow function of its argument, in contrast to  $A(\xi, \varepsilon)$  which in a Fermi liquid peaks at  $\varepsilon \approx \xi$ . When the energy dependence of  $\Phi(\xi)$  is negligible over the energy range where the spectral functions are appreciable, the second integral in Eq. (8a) reduces to the convolution of two Lorentzian functions, and the real and imaginary parts of the complex conductivity can be recast into the very convenient form<sup>12-14</sup> (Appendix A):

$$\sigma(\omega) = \frac{i\Phi(0)}{\omega} \int_{-\infty}^{\infty} d\varepsilon \frac{f(\varepsilon) - f(\varepsilon + \hbar\omega)}{\hbar\omega + \Sigma^*(\varepsilon) - \Sigma(\varepsilon + \hbar\omega)}. \quad (9)$$

Equation (9) reduces to the Drude formula Eq. (1) if we put  $\Sigma(\varepsilon) \equiv -i\hbar/(2\tau_D)$ , and if  $\Phi(0)$  is evaluated using the three-dimensional isotropic electron gas formulae.

In the context of a single-band system, the total sum rule as defined from Eq. (3) reads:

$$\epsilon_0 \omega_p^2 = \int_{-\infty}^{\infty} d\xi n(\xi) \frac{\partial \Phi}{\partial \xi} = -\frac{2e^2}{d\hbar^2} \langle n(\xi_{\mathbf{k}}) \nabla^2 E_{\mathbf{k}} \rangle_{\text{BZ}} \quad (10)$$

in which  $\langle \dots \rangle_{\text{BZ}}$  designates an average over the Brillouin zone, and  $n(\xi_{\mathbf{k}}) = \langle c_{\mathbf{k}}^\dagger c_{\mathbf{k}} \rangle = \int d\varepsilon f(\varepsilon) A(\mathbf{k}, \varepsilon)$  is the momentum distribution of the electrons. For a simple tight binding band  $E_{\mathbf{k}} \propto \sum_{\alpha} \cos k_{\alpha}$ , the right-hand side becomes proportional to the kinetic energy. Note that the value of the sum-rule thus depends on temperature and interaction strength. This is in contrast to the case where the whole solid (with all bands) is considered, in which case the plasma frequency  $\omega_p^2$  is set by the bare electron mass and total number of electrons ( $f$ -sum rule). Note also that the approximate formula (9) in which the transport function was replaced by a constant does not reproduce correctly the total sum-rule, which is expected since it is only valid at low-energy. We shall see however that it can in general be used to reliably estimate the spectral weight of the Drude peak.

### B. Scattering in a local Fermi liquid

The self-energy of a local Fermi liquid reads, at low frequency and temperature:

$$\Sigma(\varepsilon, T) = \left(1 - \frac{1}{Z}\right) \varepsilon - \frac{i}{Z\pi k_B T_0} [\varepsilon^2 + (\pi k_B T)^2]. \quad (11)$$

In this expression,  $Z$  is the quasiparticle spectral weight. In a local Fermi liquid, it is also related to the quasiparticle mass renormalization through  $Z = m/m^*$  (i.e. the quasiparticle Fermi velocity is  $v_F^* = Zv_F$ ). Close to the Fermi surface and for  $\varepsilon \ll k_B T$ , the spectral function is approximately a Lorentzian peak of weight  $Z$ , centered around  $\varepsilon = Z\xi_{\mathbf{k}}$  (the quasiparticle dispersion). We define the temperature-dependent quasiparticle lifetime from the zero-frequency value of  $\Sigma_2$  as:

$$\frac{\hbar}{\tau_{\text{qp}}} \equiv 2Z|\Sigma_2(\varepsilon = 0, T)| = 2\pi \frac{(k_B T)^2}{k_B T_0}. \quad (12)$$

It corresponds to twice the width of the Lorentzian quasiparticle peak in the spectral function, that is to the decay rate of the probability (square of the Green's function).

Fermi liquid behavior self-consistently relies on the existence of a sharp Fermi surface, and applies when the scattering rate of the typical excitation is smaller than its energy. The scattering rate  $\hbar/\tau_{\text{qp}}$  must be compared to a typical thermal excitation energy, say  $2\pi k_B T$ . The characteristic Fermi liquid energy scale  $k_B T_0$  is defined as the temperature where  $\hbar/\tau_{\text{qp}} = 2\pi k_B T$ , and will serve as a basic unit below. This is illustrated in Fig. 1 (left panel) which sketches the dependence of the quasiparticle lifetime on temperature. The temperature  $T_0$  also sets the coupling strength: a small  $T_0$  corresponds to strong electron-electron interactions and

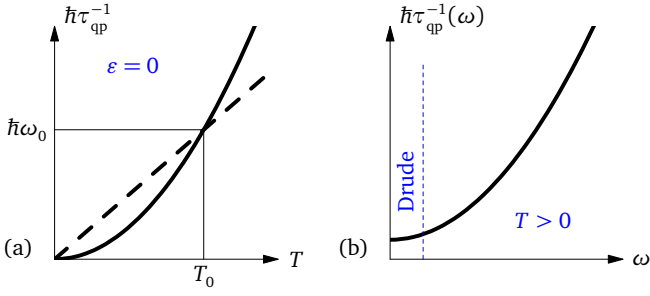


FIG. 1. Fermi liquid scattering rate  $\hbar\tau_{\text{qp}}^{-1}$ . (a) At zero energy,  $\hbar\tau_{\text{qp}}^{-1}$  increases quadratically with temperature (solid line). The dashed line indicates  $2\pi k_B T$ . The intercept defines a temperature scale  $T_0$  and a frequency scale  $\hbar\omega_0 = 2\pi k_B T_0$ . (b) At finite  $T$ ,  $\hbar\tau_{\text{qp}}^{-1}(\omega)$  increases quadratically with the frequency  $\omega$ . The applicability of the frequency-independent (Drude) approximation is limited to low frequencies.

a large value of  $\Sigma_2$ . Hence, the quasiparticle lifetime diminishes rapidly as a function of temperature and frequency. The precise relation of the scale  $T_0$  to the scale  $T_{\text{FL}}$ , below which strict Fermi liquid behavior holds, is discussed in Sec. IV. In strongly correlated (local) Fermi liquids in which  $Z$  is small, e.g. close to a Mott transition (Sec. IV) or in heavy-fermion materials, all physical quantities scale with a single energy scale, and  $T_0$  is proportional to  $\sim ZD$  (with possibly a small value of the prefactor). Here,  $D$  is the half-bandwidth of the bare band. The factor  $1/Z$  which has been pulled out in front of  $\Sigma_2$  in order to define  $T_0$  ensures that in such a case  $\Sigma_2$  is a scaling function of  $T/ZD$  and  $\varepsilon/ZD$ .

The right panel of Fig. 1 suggests that the frequency-dependence of the quasiparticle scattering rate is actually important. A Drude-like optical response with a constant relaxation time  $\tau_D \sim \tau_{\text{qp}}$  can only be expected to provide a reasonable description in the very low-frequency or relatively high-temperature regime  $\hbar\omega \lesssim 2\pi k_B T$ . When  $\hbar\omega \gtrsim 2\pi k_B T$ , the energy dependence of  $\Sigma(\varepsilon)$  cannot be neglected and a non-Drude response arises, as discussed in the following section.

We finally note that a real, frequency-independent Hartree term  $\Sigma_1(0, T)$  should in fact be added to Eq. (11) for completeness. It sets the location of the Fermi surface from  $E_k = \mu - \Sigma_1(0, T)$  and can be viewed as a shift of the chemical potential, which will be omitted for simplicity in all equations. An imaginary frequency-independent part can also be added, to mimic the effects of the impurity scattering. This is considered in Appendix E.

### C. Scaling form of the optical conductivity in a local Fermi liquid

We now show that the optical conductivity obeys a universal scaling form in terms of the two variables  $\omega\tau_{\text{qp}}$  and  $\hbar\omega/(2\pi k_B T)$ . Whereas it reduces essentially to the Drude form in the low-frequency limit, its full frequency depen-

dence is markedly different.

The universal scaling form is derived by inserting Eq. (11) into Eq. (9). The calculations can be performed analytically and yield:

$$\sigma(\omega) = \sigma_{\text{dc}} \mathcal{S} \left( \frac{\hbar\omega}{2\pi k_B T}, \omega\tau_{\text{qp}} \right) \quad (13a)$$

$$\sigma_{\text{dc}} = \frac{\pi^2}{12} Z \Phi(0) \tau_{\text{qp}} \quad (13b)$$

$$\mathcal{S}(x, y) = \frac{6}{\pi^2 x} \int_{-\infty}^{\infty} du \frac{[e^{\pi(u-x)} + 1]^{-1} - [e^{\pi(u+x)} + 1]^{-1}}{1 + x^2 - iy + u^2}.$$

The scaling function  $\mathcal{S}$  is evaluated and displayed in Appendix B. One obtains:

$$\mathcal{S}(x, y) = \frac{6i}{\pi^2 x} \frac{1}{r(x, y)} \left\{ \psi \left( \frac{1}{2} [1 + r(x, y) - ix] \right) - \psi \left( \frac{1}{2} [1 + r(x, y) + ix] \right) \right\}, \quad (13c)$$

where  $r(x, y) = \sqrt{1 + x^2 - iy}$  and  $\psi$  is the digamma function defined as  $\psi(z) = \lim_{M \rightarrow \infty} [\log M - \sum_{n=0}^M 1/(n+z)]$ .

Equation (13a) emphasizes the emergence of two natural time/frequency scales: the quasiparticle time  $\tau_{\text{qp}}$ , and a “coherence” time  $\hbar/(2\pi k_B T)$ . Alternatively, one can reexpress

$$\sigma(\omega) = \sigma_{\text{dc}} \mathcal{S} \left( \frac{\bar{\omega}}{\bar{T}}, \frac{\bar{\omega}}{\bar{T}^2} \right) \quad (14)$$

with  $\bar{\omega} \equiv \hbar\omega/(2\pi k_B T_0)$  and  $\bar{T} \equiv T/T_0$  dimensionless variables normalized to the basic scale  $T_0$ . This emphasizes that the optical conductivity in a Fermi liquid is a scaling function of  $\omega/T$  and  $\omega/T^2$ . Equations (13) constitute the key analytical result of this article. They replace the Drude formula by a universal scaling form of these *two* frequency scales, which is valid for local Fermi liquids. Let us emphasize that all high-energy scales such as the bare bandwidth or the plasma frequency  $\omega_p$  have disappeared from the scaling expression (13a). Instead, only low-energy scales appear, such as  $T_0$  and  $Z\Phi(0)$  (the latter is shown below to be related to the low-energy Drude weight).

In Fig. 2, we plot the real and the imaginary parts of  $\sigma(\omega)/\sigma_{\text{dc}}$  as a function of  $\hbar\omega/(2\pi k_B T)$  on a log-log scale at a given low temperature  $T/T_0 = 0.1$ . (The full frequency and temperature dependence is shown on a three-dimensional plot in Appendix B.) Three frequency regimes can be identified from this plot:

- At low-frequency  $\omega \lesssim \omega_L < 2\pi k_B T/\hbar$  (with  $\omega_L$  to be made precise below, of order  $\tau_{\text{qp}}^{-1}$  at low temperature) the conductivity follows closely the Drude model, with a saturation of  $\sigma_1$  below the characteristic frequency  $\tau_{\text{qp}}^{-1}$  and a  $1/\omega^2$  decay above it.  $\tau_{\text{qp}}^{-1}$  also separates the dissipative regime (with larger  $\sigma_1$ ) from the inductive regime (with larger  $\sigma_2$ ).
- When  $\omega$  approaches  $2\pi k_B T/\hbar$ , the conductivity deviates from the Drude behavior:  $\sigma_1$  displays a

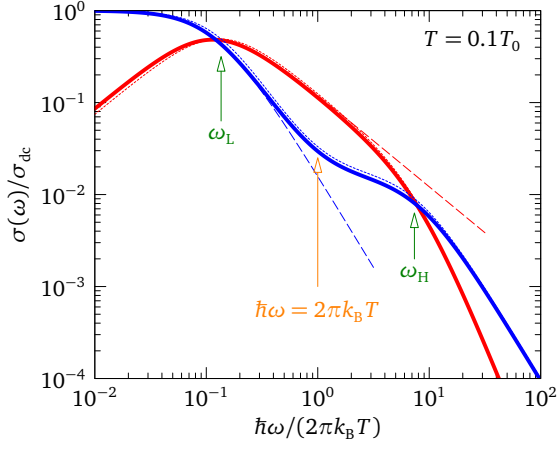


FIG. 2. Fermi-liquid conductivity Eqs. (13) at low temperature (solid lines), below the temperature  $T_1$  defined in Fig. 3. The blue (red) lines show the real (imaginary) part of the conductivity. The dashed lines show the low-frequency Drude-like behavior given by Eq. (15). The dotted lines show Eq. (18). The characteristic frequency scales  $\omega_L$  and  $\omega_H$  correspond to those defined in Fig. 3 and Eq. (20).

pronounced shoulder with much weaker frequency dependence—the feature appears as a shoulder in a log-log plot, as a ‘foot’ in a lin-lin plot, see below. In this ‘thermal’ regime, the conductivity behaves inductively ( $\sigma_2 > \sigma_1$ ) rather than dissipatively.

- Increasing  $\omega$  further,  $\sigma_2$  decays more rapidly, and at  $\omega_H$  (to be defined below) the data become dissipative-like again ( $\sigma_1/\sigma_2 > 1$ ). This is actually a consequence of the assumed unbounded quadratic increase of the scattering rate with frequency, and might not be physical in this already high frequency regime (see Sec. IV). Above  $\omega_H$ ,  $\sigma_1$  recovers a Drude-like  $1/\omega^2$  decay, while  $\sigma_2$  turns to  $1/\omega^3$ . The  $1/\omega^3$  behavior is an artifact of extending the  $\omega^2$  in the self-energy Eq. (11) to high energies.<sup>15</sup>

These different regimes, as well as the precise conditions determining the characteristic frequencies  $\omega_{L,H}$  are represented on Fig. 3. We now discuss these different regimes in more details.

#### D. Drude regime

The lowest frequency regime can legitimately be called ‘Drude regime’, since there the frequency-dependence of the scattering rate can be ignored. In this regime, the frequency  $\hbar\omega$  is small with respect to  $2\pi k_B T$ , the inverse quasiparticle time  $\tau_{qp}^{-1}$  is smaller than, or comparable to the temperature, but the product  $\omega\tau_{qp} \equiv y$  can take arbitrary values (Fig. 3). This regime is thus described by taking the limit

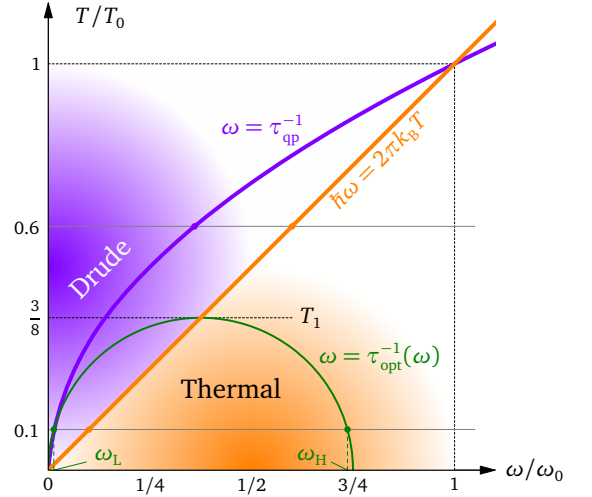


FIG. 3. Regimes of conduction. The Drude regime applies if  $\omega < 2\pi k_B T/\hbar$ , and the thermal regime if  $\omega \gtrsim 2\pi k_B T/\hbar$ . The conductivity along the two horizontal cuts at fixed temperature is displayed in Figs. 2 and 6.

$x \equiv \hbar\omega/(2\pi k_B T) \rightarrow 0$  in the scaling form (13c). This yields:

$$\frac{\sigma(\omega)}{\sigma_{dc}} \approx \frac{6}{\pi^2} \frac{\psi' \left( \frac{1}{2} \left[ 1 + \sqrt{1 - i\omega\tau_{qp}} \right] \right)}{\sqrt{1 - i\omega\tau_{qp}}} \quad (15)$$

where  $\psi'$  is the derivative of the digamma function. This is shown as the dashed lines in Fig. 2. Interestingly, this expression differs from the simple Drude form  $\sigma(\omega)/\sigma_{dc} = 1/(1 - i\omega\tau_D)$ . However, as detailed in Appendix C, the frequency dependence of the exact expression (15) can be rather accurately approximated by the simple Drude form, provided  $\tau_D$  is chosen in an appropriate manner (which is such that  $\tau_D$  differs from  $\tau_{qp}$  however).

The spectral weight in the Drude peak can be estimated as:

$$\frac{2}{\pi} \int_0^{\omega_D} d\omega \sigma_1(\omega) = Z\Phi(0) \quad (16)$$

in which  $\omega_D$  is a cutoff defining the Drude regime. This expression can be established in two ways. The first is to perform a direct frequency integration of the scaling expression (15) over the whole frequency range (i.e. for the scaling variable  $y = \omega\tau_{qp}$  varying from 0 to  $\infty$ ). Alternatively, since  $\Phi(\xi)$  can be taken as constant in the low-frequency range, one can use expression (9) and observe that it yields a high-frequency behavior of  $\sigma_2 \sim Z\Phi(0)/\omega$ . By Kramers-Kronig, this leads to Eq. (16).

Two remarks are in order regarding expression (16). First, the Drude weight scales with the quasiparticle weight  $Z$ . Close to a Mott transition, for example,  $Z$  is expected to vanish and so does the Drude weight. Second, it should be noted that  $Z$  measures the renormalization of the Drude weight as compared to the non-interacting (band) value  $\Phi(0)$  and *not* the spectral weight of the Drude peak relative

to the total integrated spectral weight  $\epsilon_0 \omega_p^2$ . The latter relative weight is given by  $Z\Phi(0)/\epsilon_0 \omega_p^2 \approx \mathcal{D}(0)$  with  $\epsilon_0 \omega_p^2$  given by Eq. (10).

### E. Thermal regime and emergence of the $2\pi$ factor in the optical scattering rate

In the thermal regime,  $\hbar\omega$  is comparable to  $2\pi k_B T$  and  $\omega\tau_{qp} \gg 1$ . This corresponds to the limit of fixed  $x = \hbar\omega/(2\pi k_B T)$  and large  $y = \omega\tau_{qp} \gg x$ . The scaling function  $\mathcal{S}(x, y)$  has the following expansion for  $y \rightarrow \infty$ :

$$\mathcal{S}(x, y \rightarrow \infty) = \frac{12i}{\pi^2 y} + \frac{16}{\pi^2 y^2} (1 + x^2). \quad (17)$$

Using this expression and performing a large- $y$  expansion of  $1/\sigma = 1/[\sigma_{dc}\mathcal{S}(x, y)]$ , one directly obtains a generalized Drude form for the optical conductivity:

$$\sigma(\omega) \approx \frac{Z\Phi(0)}{-i\omega + 1/\tau_{opt}(\omega)} \quad (18)$$

with the optical scattering rate:

$$\frac{\hbar}{\tau_{opt}(\omega)} = \frac{2}{3\pi k_B T_0} [(\hbar\omega)^2 + (2\pi k_B T)^2]. \quad (19)$$

The same result is found by approximating  $\mathcal{D}(\omega)$  in Eq. (5) by  $\mathcal{D}(0) \approx Z\Phi(0)/(\epsilon_0 \omega_p^2)$ , identifying with Eqs. (13), and expanding for large  $y$ . Eq. (18) is displayed in Fig. 2 as the dotted lines. While the Fermi-liquid form of the quasiparticle lifetime (a one-particle quantity) involves  $(\hbar\omega)^2 + (\pi k_B T)^2$ , it should be emphasized that the optical scattering rate (a two-particle quantity) involves instead a factor  $2\pi$  in the combination  $(\hbar\omega)^2 + (2\pi k_B T)^2$ . This seems to have been first emphasized by Gurzhi.<sup>16</sup> Experimentally, the  $2\pi$  factor has not been observed so far in simple metals. As discussed in details in Sec. V, in several correlated metals a scaling of the optical scattering rate following  $(\hbar\omega)^2 + (p\pi k_B T)^2$  was reported, with values of  $p$  ranging from 1 to 2.4.<sup>17–22</sup> The departure from the Fermi-liquid value  $p = 2$  may be attributed to scattering mechanisms with a different frequency/temperature dependence.<sup>4,5</sup> In Appendix E, we show that a frequency-independent scattering rate does not change the value  $p = 2$ .

At low temperature, Eqs. (18) and (19) allow to define two characteristic frequencies  $\omega_{L,H}$  from the condition  $\omega = \tau_{opt}^{-1}(\omega)$ , or equivalently  $\sigma_1(\omega) = \sigma_2(\omega)$ :

$$\hbar\omega_{L,H} = \frac{3}{4}\pi k_B T_0 \left[ 1 \pm \sqrt{1 - \left(\frac{8T}{3T_0}\right)^2} \right]. \quad (20)$$

Plotted as a function of  $T$ , these two frequencies form a dome in the  $(\omega, T)$  plane, defining the thermal regime (green line in Fig. 3). Below this dome, the conductivity behaves inductively. While the scales  $\omega_{L,H}$  can be determined

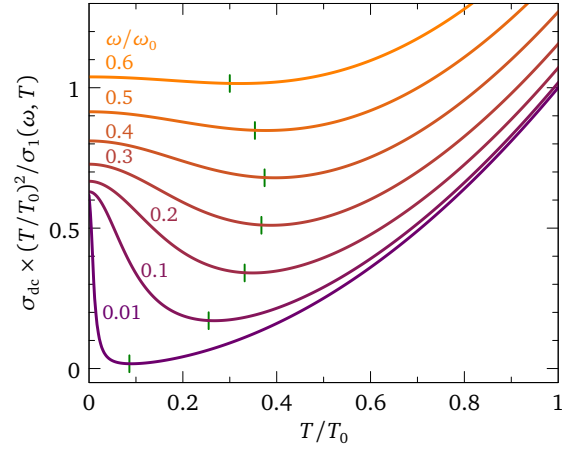


FIG. 4. Ac resistivity  $1/\sigma_1(\omega, T)$  as a function of  $T$  for several frequencies  $\omega$ . These curves correspond to vertical slices in Fig. 3, and the green bars indicate the temperature at which the dome is crossed for each frequency. The temperatures are measured in units of  $T_0$ , and the frequencies in units of  $\omega_0 = 2\pi k_B T_0/\hbar$ . The normalization of the resistivity is  $\sigma_{dc}(T/T_0)^2 = \pi\hbar Z\Phi(0)/(24k_B T_0)$ .

from the crossings of  $\sigma_1$  and  $\sigma_2$  plotted as a function of frequency (Fig. 2), the crossing of the dome is most easily identified by a minimum in a plot of  $1/\sigma_1(\omega, T)$  as a function of  $T$ , at a fixed finite frequency. This is illustrated in Fig. 4. As this determination of  $\omega_{L,H}$  only relies on  $\sigma_1$ , it might be the most direct way of checking FL behavior in experimental datasets.

Finally, we plot in Fig. 5 the imaginary part of the memory function, defined according to Eq. (2) with the conductivity given by the Fermi-liquid expressions (13). Fig. 5a displays the crossover from the Drude to the thermal regime.  $M_2(\omega)$  increases quadratically for  $\omega \rightarrow 0$ , with a temperature-dependent curvature given in Appendix D. In the thermal

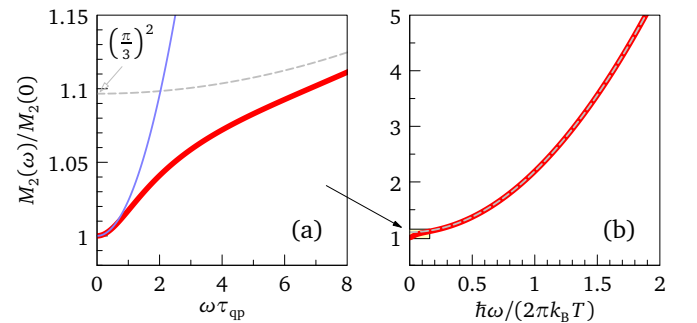


FIG. 5. Imaginary part of the memory function in a Fermi liquid at  $T = 0.02T_0$  (thick red lines). (a) At frequencies  $\omega < \tau_{qp}^{-1}$ ,  $M_2(\omega)$  increases as  $\omega^2$  (thin blue line), with a temperature-dependent curvature given by Eq. (D2). (b) In the thermal regime,  $M_2(\omega)/M_2(0)$  scales as  $(\pi/3)^2(1 + x^2)$  with  $x = \hbar\omega/(2\pi k_B T)$  (dashed line).

regime, the expansion (17) leads to the following form:

$$M(\omega) \approx \left( \frac{\epsilon_0 \omega_p^2}{Z\Phi(0)} - 1 \right) \omega + i \frac{\epsilon_0 \omega_p^2}{Z\Phi(0)} \frac{2}{3\pi\hbar k_B T_0} [(\hbar\omega)^2 + (2\pi k_B T)^2]. \quad (21)$$

The imaginary part is shown in Fig. 5b. At  $\omega = 0$ , Eq. (21) extrapolates to a value larger than the exact value  $iM_2(0)$  by a factor  $(\pi/3)^2$  (see Appendix D). Similarly, the approximations (18) and (19) for the conductivity deviate slightly from the exact conductivity in the limit  $\omega \rightarrow 0$ . Setting  $\omega = 0$  in these equations yields  $\sigma(0) = (3/\pi)^2 \sigma_{dc}$ . All these observations are due to the fact that the expressions (19) and (21) holds in the thermal regime, but are not accurate at very low frequency.

### E Coherent and “incoherent” regimes

It is seen from Fig. 3 that the three frequency scales  $\omega_{L,H}$  and  $2\pi k_B T/\hbar$  defined above merge when the temperature is raised above  $T_1 = 3T_0/8$ . Above  $T_1$ , an “incoherent” regime is found in which the thermal scale  $2\pi k_B T/\hbar$  becomes the only characteristic frequency scale and  $\sigma_2$  becomes smaller than  $\sigma_1$  at all frequencies, because  $\tau_{opt}^{-1} > \omega$  (see Fig. 6). The term incoherent is put in quotes, because at such a high temperature  $T \sim T_0$  the scaling form of the self-energy may be no longer valid. The actual incoherent regime occurs due to the breakdown of the Fermi liquid form Eq. (11) altogether. The question whether the scaling form applies is then irrelevant.

The reciprocal argument, on the other hand, is valid. Observing two frequencies at which  $\sigma_1 = \sigma_2$  indicates that the Fermi liquid range has been reached. On a log-log plot of  $\omega\sigma_1(\omega)$  versus  $\omega$ , these two crossing points coincide with two symmetric maxima located at  $\omega_{L,H}$ , separated by a minimum at  $\omega = 2\pi k_B T/\hbar$ .

## IV. OPTICAL CONDUCTIVITY OF A HOLE-DOPED MOTT INSULATOR WITHIN DYNAMICAL MEAN-FIELD THEORY

### A. Model and methods

In this section, we present calculations of the optical conductivity for a specific microscopic model, the single band Hubbard model of a hole-doped Mott insulator. The calculations are performed within single-site dynamical mean-field theory (DMFT).<sup>23</sup> As we shall see, the universal scaling form derived above allows one to identify specific signatures of Fermi-liquid behavior in the DMFT optical conductivity, which have not been emphasized previously. Conversely, the model calculation allows for a test of the scaling theory, and especially of its range of validity as a function of frequency and temperature. Optical conductivity has been calculated with DMFT by several authors in various contexts (see e.g.

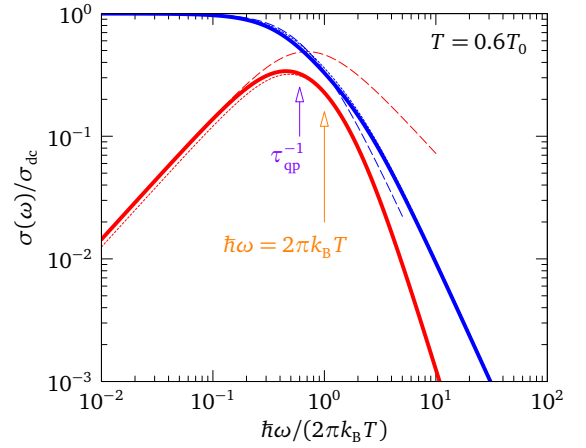


FIG. 6. Fermi-liquid conductivity Eqs. (13) at high temperature (solid lines), above the temperature  $T_1$  defined in Fig. 3. The blue (red) lines show the real (imaginary) part of the conductivity. The dashed lines show the low-frequency Drude-like behavior given by Eq. (15). The dotted lines show Eq. (18).

Refs. 24 and 25, and, for a review and more references, Ref. 8). However, an explicit analysis in connexion with FL scaling laws has not been made, and requires calculations with very high accuracy solvers at low energy, which became available only recently.

A semicircular density of states with half-bandwidth  $D$  has been used, and the model is considered in its paramagnetic phase. The DMFT equations were solved using highly accurate continuous-time quantum Monte Carlo (CT-QMC)<sup>26,27</sup> and numerical renormalization group<sup>28,29</sup> (NRG) solvers. The imaginary-frequency data from Monte Carlo were analytically continued using Padé approximants. Excellent quantitative agreement between the data obtained using the two techniques was achieved in a broad temperature and frequency range. At the lowest temperatures (below  $k_B T/D = 0.01$ ) and the lowest frequencies, however, artifacts associated with the discretization of the energy mesh and spectral broadening become visible in the NRG data, and the CT-QMC+Padé method becomes preferable. Conversely, the CT-QMC+Padé data becomes less accurate at higher temperatures  $k_B T/D > 0.05$ , especially for larger frequencies  $\hbar\omega/D > 1$ . The data used here are obtained by taking the low frequency part ( $\hbar\omega/D < 0.15$ ) from the calculation based on the CT-QMC+Padé self-energies, and the high-frequency part ( $\hbar\omega/D > 0.15$ ) from the NRG self-energies, with perfect matching in the intermediate region.

### B. Self-energy, local Fermi-liquid behavior, and key temperature scales

The analysis presented here is based on the DMFT dataset used earlier in Ref. 30. There, transport and thermodynamic properties were discussed in detail, but only some aspects of the optical conductivity were addressed. For convenience, we restate here the key temperature scales identified in this

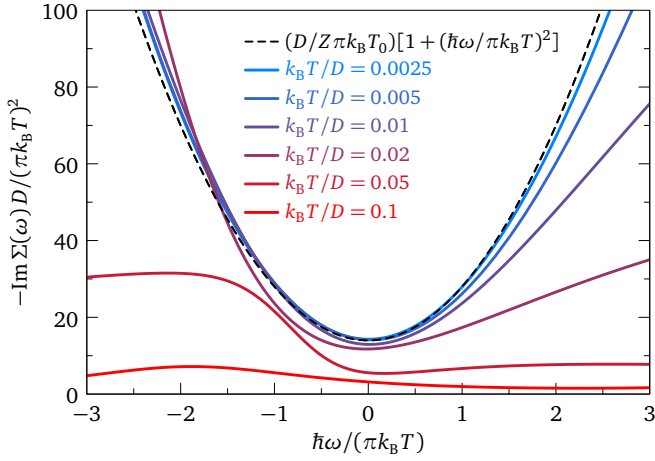


FIG. 7. DMFT self-energy scaling plot. At low temperatures, the curves collapse to a parabola. By comparing with Eq. (11) and taking into account that one has  $Z = 0.22$  for a doping  $\delta = 0.2$ , one can determine  $k_B T_0 \approx 0.1D \approx 10k_B T_{FL}$ .

previous work, as well as their evolution with doping. The actual data considered in detail later in the present paper are for a doping level  $\delta = 20\%$  and a coupling  $U/D = 4$  (at which the undoped system is a Mott insulator), but we mention the doping evolution of the key quantities.

The quasiparticle weight  $Z$  was found to be approximately equal to the doping level  $Z \approx \delta$  (more precisely,  $Z = 0.22$  was found for  $\delta = 0.2$ ). A temperature scale of key importance is the Fermi-liquid temperature scale  $T_{FL}$ . This was defined as the temperature below which the  $T^2$  behavior of the resistivity and the  $\omega/T$  scaling of the self-energy apply. From the DMFT data, this scale was identified as  $T_{FL} = 0.05\delta D$ , which gives  $0.01D$  for  $\delta = 0.2$ , a very low energy scale. In the same work,<sup>30</sup> the quasiparticle features in the spectra were shown to persist to a much higher temperature,  $\delta D$ . Important particle-hole asymmetry was found in many physical properties. At a scale approximately equal to  $\delta D$ , these ‘resilient quasiparticles’ disappear and the system becomes an incoherent ‘bad metal’ with a resistivity which becomes larger than the Mott-Ioffe-Regel value. It should be emphasized that the Fermi-liquid scale  $T_{FL}$  is one order of magnitude smaller than the scale at which the crossover into the bad-metal regime occurs. The latter corresponds quite accurately to the Brinkman-Rice scale  $\sim \delta D$ , which corresponds to the renormalized kinetic energy of the quasiparticles and is much larger than  $T_{FL}$  (although both scales are proportional to the doping level).

In Fig. 7, we display the imaginary part of the self-energies  $\Sigma$ , as a scaling plot  $-\text{Im}\Sigma(\omega)D/(\pi k_B T)^2$  versus  $\hbar\omega/(\pi k_B T)$ . The data nicely obey the Fermi-liquid law  $\propto 1 + (\hbar\omega/\pi k_B T)^2$  at low temperatures. By comparing with the prefactor of this scaling behavior as defined in Eq. (11), one determines the scale  $T_0$  to be (at  $\delta = 20\%$ ):  $k_B T_0 \approx 0.1D$ , so that  $T_0 \approx 10T_{FL}$ . For an arbitrary doping level, one finds,  $k_B T_0 \approx 0.57\delta D$ . The scale  $T_0$  is thus rather close in magnitude to the Brinkman-Rice scale, while  $T_{FL}$  is

an order of magnitude smaller. Therefore, when analyzing the DMFT results in the light of Fig. 3 and of the scaling analysis, it should be remembered that FL behavior actually fully applies only below  $T_{FL} = 0.1T_0$ .

At higher temperatures, deviations from FL rapidly appear for electron-like ( $\omega > 0$ ) single-particle excitations (Fig. 7). There, the deviations from the parabolic form become substantial at a frequency  $\hbar\omega_+ \approx \pi T_{FL}$ , where the real part of the self-energy (not shown, see Ref. 30) displays a kink. For hole-like excitations ( $\omega < 0$ ), the parabolic behavior is more robust, and the kink appears only at  $\omega_- \approx 0.2D$ . The transport (resistivity, thermopower) probes a frequency window of a few  $k_B T$ , and these quantities deviate from the FL universal behavior when  $k_B T > \hbar\omega_+$ .

### C. Optical conductivity at low temperature

Fig. 8 for  $T = T_{FL}/4 = T_0/40$  demonstrates that the optical conductivity of the hole-doped Hubbard model obtained from DMFT is very well described by the universal FL scaling form (13) derived in the previous section, in the low-frequency and low-temperature regime. This is indeed expected from the previous figure demonstrating FL scaling of the single-particle self-energy.

When looking at  $\sigma_1(\omega)$  on a lin-lin scale (Fig. 8a), the narrow Drude peak at low-frequency is followed at higher frequency  $\hbar\omega \sim 2\pi k_B T$  by a characteristic non-Drude ‘foot’. On a log-log plot (Fig. 8b), this appears as a shoulder. This does not signal non-Fermi liquid physics, as one might naively think, but is actually a key feature of FL theory which signals the onset of the thermal regime at  $\hbar\omega \sim 2\pi k_B T$ . The non-Drude foot/shoulder is thus, somewhat counterintuitively, a striking signature of Fermi-liquid behavior.

At higher frequencies, the DMFT data displays two peaks. The first one, for  $\hbar\omega \approx 0.5D$  (corresponding typically to the

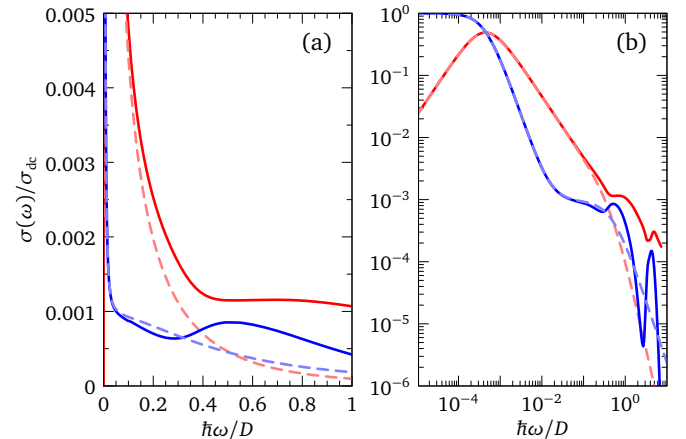


FIG. 8. Comparison of the optical conductivity at  $k_B T/D = 0.0025D$  ( $T = T_{FL}/4$ ) for the doped Hubbard model calculated within DMFT (solid lines) to the universal FL scaling form (dashed lines). The real (blue) and imaginary (red) parts are plotted on a lin-lin (a) and log-log (b) scale.

mid-infrared MIR regime) is associated with the transitions between the quasiparticle band and the lower Hubbard band. The high-frequency peak at  $\hbar\omega \approx 4D \sim U$  corresponds to the transitions to the upper Hubbard band. These peaks are, obviously, not present in the FL expressions. Likewise, at the highest frequencies the bare particle dynamics (with  $\sigma_2 \propto 1/\omega$ ) is recovered in the DMFT data, whereas extrapolating FL behavior to infinite frequencies would lead to the incorrect behavior  $\sigma_2 \propto 1/\omega^3$ .

#### D. Memory function

More subtle corrections to the FL are seen in the DMFT data, also at frequencies smaller than the MIR, in the ‘foot/shoulder’ region (but above the low-frequency kink of the self-energy). To resolve them more clearly, it is convenient to look at the memory function. In Fig. 9 we plot the memory function at a low temperature  $T = T_{\text{FL}}/4$ .

The memory function has features on crossing the Hubbard bands (Fig. 9a), which we will not discuss here. Below the MIR scale (Fig. 9b), approximately linear and quadratic behaviors are seen for the real and imaginary parts, respectively (Fig. 9c). On zooming up further (Fig. 9d), one sees an excellent agreement between the DMFT results and the FL scaling form, including the small crossover at the lowest

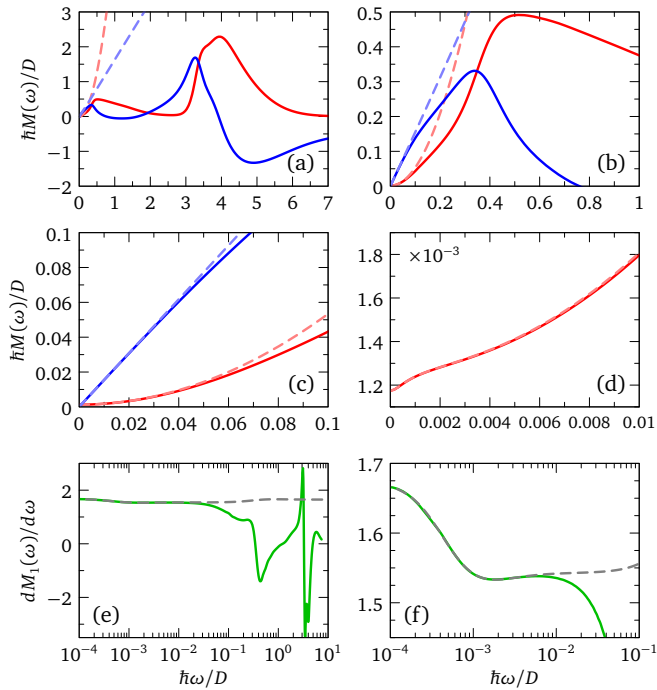


FIG. 9. Memory function at  $k_B T/D = 0.0025$  ( $T = T_{\text{FL}}/4$ ). (a)–(d): real (solid blue) and imaginary (solid red) parts of the memory function, compared with the FL scaling forms (dashed). The data are shown for several frequency windows ranging from a very broad one (a), to a very narrow one (d). Panels (e) and (f) show the frequency derivative of  $M_1$  (solid lines) compared with the FL expressions (dashed lines).

frequencies  $\omega = 1/\tau_{\text{qp}} \approx 0.001$ .

Whereas agreement between the DMFT data and the FL scaling form is perfect at the lowest frequencies, some deviations appear at a small but well-defined and important FL frequency scale, the frequency  $\omega_+ \approx 0.03$  associated with the positive-energy (electron-like) ‘kink’. This is seen clearly in  $M_2$  or the derivative  $dM_1/d\omega$  (Fig. 9e and f). The deviation from the FL form goes into the direction of a smaller memory function. This is due to the fact that, in the hole-doped Hubbard model studied here, the positive frequency ‘resilient quasiparticles’ scatter less than the parabolic behavior from Landau FL theory would predict. We stress that, for the hole-doped Hubbard model, the corresponding deviation cannot be observed in photoemission spectroscopy, since they appear at positive excitation energies. Optical spectroscopy, because it probes particle-hole excitations, is thus a powerful tool which could probe the existence of these resilient quasiparticles. Moreover, combining photoemission with precise optical spectroscopy could be used to reveal the strong particle-hole asymmetry of these excitations. Signatures of the low-frequency kink from optical spectroscopy would also be very interesting.

#### E. Temperature-dependence of the optical conductivity

Finally we discuss the evolution of the optical conductivity at higher temperatures. Fig. 10 displays  $\sigma_1(\omega)$  for several temperatures ( $D/k_B T = 400, 200, 100, 50, 20, 10$ ). The DMFT data are compared to the analytical form dictated by the FL scaling function, in which  $\tau_{\text{qp}}$  is determined from the FL  $T^2$  dependence. The difference between the FL and the DMFT becomes pronounced for  $T \gtrsim T_{\text{FL}}$ . Note that a milder frequency dependence is seen above  $T_{\text{FL}}$ , both in the FL and DMFT (in the former it occurs due to the narrowing of the thermal crossover foot/shoulder). This warns again that interpreting apparent non-Drude power laws as a signature of non-Fermi liquid behavior is a risky enterprise.

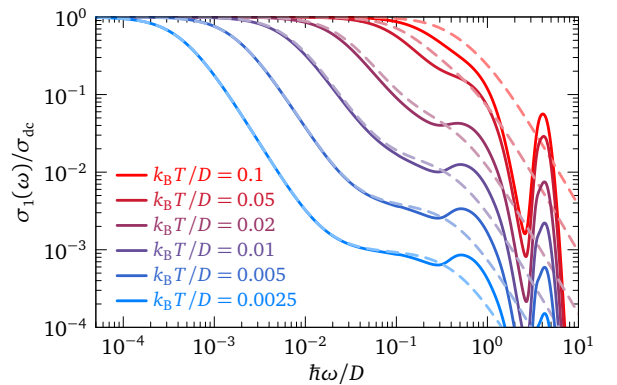


FIG. 10. Comparison of the real part of the optical conductivity in the Hubbard model from DMFT (solid lines) with the analytical FL scaling expressions (dashed lines). Inverse temperatures are  $D/k_B T = 400, 200, 100, 50, 20, 10$ .

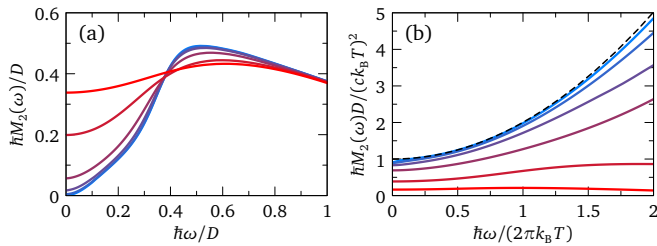


FIG. 11. (a) Temperature dependence of the imaginary part of the memory function in DMFT. The temperatures and the color code are the same as in Fig. 10. (b) Scaling plot. The  $\hbar\omega/(2\pi k_B T)$  scaling applies at low temperatures and intermediate frequencies. The dashed line shows the parabolic behavior corresponding to Eq. (21).

In Fig. 11, we show the temperature evolution of the imaginary part of the memory function. In Fig. 11b the data are plotted as  $M_2/T^2$  versus  $\omega/T$ . This reveals clearly the scaling behavior, consistent with the  $(\hbar\omega)^2 + (2\pi k_B T)^2$  dependence in the thermal regime of FL theory.

At low  $T$ , FL deviations from the quadratic dependence on frequency are seen at the lowest frequencies, indicating the onset of the Drude regime where  $\hbar\omega \ll 2\pi k_B T$ . On the high energy side, the discrepancies are seen above  $\omega_+$ . Above  $T_{FL}$  the data deviates from a parabola and the  $\omega/T$  FL scaling does not apply anymore.

## V. IMPLICATIONS FOR EXPERIMENTS

In this section, we address the implications for the experimental optical signatures of Fermi-liquid behavior, in the light of the theoretical results discussed in Sec. III. We will also discuss what has been obtained until now in a number of materials, in particular the heavy-fermion materials CePd<sub>3</sub>, UPd<sub>2</sub>Al<sub>3</sub>, and URu<sub>2</sub>Si<sub>2</sub>, heli-magnetic MnSi, the organic conductor  $\kappa$ -(BEDT-TTF)<sub>2</sub>Cu[N(CN)<sub>2</sub>]Br<sub>x</sub>Cl<sub>1-x</sub>, the doped semiconductor SrTiO<sub>3</sub>, and the doped Mott-Hubbard insulator HgBa<sub>2</sub>CuO<sub>4+δ</sub>. We will see that the experimental optical data published until now do not provide a sufficiently broad spectral range to distinguish all of the optical features of a Fermi liquid. The first signature is the ‘foot/shoulder’, illustrated in Figs. 2 and 8, which marks the deviation from a low-frequency Drude-like behavior. This feature occurs at the frequency  $\omega \sim 2\pi k_B T/\hbar$ —in-between two frequencies where the imaginary and real parts of the conductivity are equal—and disappears as the temperature is raised above  $T_1$  (Figs. 3 and 6). The second signature is the characteristic frequency/temperature scaling of the optical relaxation rate shown in Eq. (19), or the equivalent behavior of the memory function given in Eq. (21). While the first signature can in principle be observed in the raw data, the second requires a determination of the spectral weight, in order to invert the complex conductivity. A third signature—present in the raw data—is the minimum in  $1/\sigma_1$ , when plotted as a function of temperature at finite frequency (Fig. 4).

Experimentally, the most direct clue of Fermi-liquid

physics is a  $T^2$  law in the resistivity. This is usually observed between a ground-state ordering temperature  $T_c$ , and a scale  $T_{FL}$  above which additional scattering mechanisms contribute to the resistivity with a different temperature dependence. For  $T_c < T < T_{FL}$ , the Fermi-liquid signatures are expected in the conductivity (provided  $T < T_1 = 3T_0/8$ ) around the frequency  $\nu = k_B T/\hbar$ , which is  $\sim 1.3$  THz for  $T = 10$  K, corresponding to  $44$  cm<sup>-1</sup>. The signature may be masked by optical phonons—with energies typically above 5 meV, i.e. 1 THz or  $40$  cm<sup>-1</sup>—and inter-band transitions. Another possible limitation is impurity scattering, which reduces the value of  $T_1$  as discussed in Appendix E.

Fermi-liquid behavior of the dc resistivity has been reported in a variety of materials. Using a bolometric direct absorption technique, Webb *et al.*<sup>31</sup> observed the narrow zero-frequency mode corresponding to the Drude peak for CePd<sub>3</sub>. The presence of the peak was also indicated by Awashti *et al.*<sup>32</sup> using resonant cavities for three discrete frequencies (for an extensive review of optical properties of heavy-electron compounds, including Fermi-liquid aspects, see Ref. 33).

UPd<sub>2</sub>Al<sub>3</sub> is a heavy-fermion material with a mass enhancement of 66.<sup>34</sup> The  $5f$  moments order anti-ferromagnetically below 14.3 K,<sup>35</sup> and a superconducting phase coexisting with the magnetic order develops below 2 K. In the temperature range between these two transitions, the resistivity increases as  $T^2$  with a typical coefficient  $A \sim 1 \mu\Omega \text{ cm}/\text{K}^2$ , suggesting Fermi-liquid behavior of the charge carriers<sup>36,37</sup> with a  $T_{FL}$  of the order of 15 K. For this material,  $\sigma(\omega)$  has been measured in the range from  $0.002$  to  $1.3$  cm<sup>-1</sup> using a coaxial technique in Corbino geometry.<sup>38</sup> Figure 12 shows the microwave data of Ref. 38, measured at  $T = 2.75$  K, well below  $T_{FL}$ . The conductivity can be well fitted to the Drude model Eq. (1), with the parameters  $\sigma_{dc} = 0.105 (\mu\Omega \text{ cm})^{-1}$  and  $\tau_D = 4.7 \times 10^{-11}$  s. This led the authors to the conclusion that impurity scattering dominates in this frequency range.

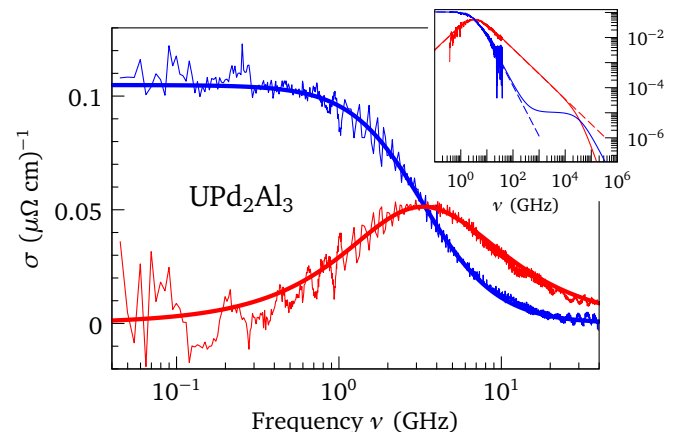


FIG. 12. Microwave optical response of UPd<sub>2</sub>Al<sub>3</sub> at  $T = 2.75$  K. The thin lines show the measurements of Ref. 38. The solid lines show a fit to Eqs. (13) with the parameters  $T_0 = 350$  K and  $Z\Phi(0) = \epsilon_0(1.6 \times 10^{14} \text{s}^{-1})^2$ . Inset: same data on a wider frequency range. The dashed lines show the Drude model.

However, the extrapolated dc resistivity of  $\sim 9 \mu\Omega \text{ cm}$  is of the order  $AT^2$ , which may also indicate that electron-electron scattering dominates the dc resistivity. As a matter of fact, the data can be equally well fitted to the Fermi-liquid formula (13), as shown in Fig. 12. This provides an alternative interpretation for the success of the Drude model: the scattering rate is due to electron-electron interactions, but it is dominated by the temperature in this low-frequency range. At the experimental temperature  $T = 2.75 \text{ K}$ , the thermal regime where deviations from the Drude model due to the frequency dependence of the scattering rate are expected, is around  $k_B T / \hbar = 360 \text{ GHz}$  (inset of Fig. 12). Note that again  $T_{\text{FL}}$  is an order of magnitude smaller than the value  $T_0 \sim 350 \text{ K}$  resulting from the fit in Fig. 12.

Recently, Nagel *et al.*<sup>22</sup> reported optical data for  $\text{URu}_2\text{Si}_2$ , exhibiting the  $1/\tau_{\text{opt}}(\omega, T) \propto (\hbar\omega)^2 + (p\pi k_B T)^2$  dependence of the optical scattering rate with  $p \approx 1$ , i.e. well below  $p = 2$  expected for a Fermi-liquid (Eq. 19). To our knowledge, the two cases in which a value of  $p$  closest to 2 has been observed are the  $\kappa$ -(BEDT-TTF)<sub>2</sub>Cu[N(CN)<sub>2</sub>]Br<sub>x</sub>Cl<sub>1-x</sub> organic compound ( $p \approx 2.4$ )<sup>39</sup> and the underdoped  $\text{HgBa}_2\text{CuO}_{4+\delta}$  ( $p \approx 1.5$ ).<sup>21</sup> The optical conductivity of  $\kappa$ -(BEDT-TTF)<sub>2</sub>Cu[N(CN)<sub>2</sub>]Br<sub>x</sub>Cl<sub>1-x</sub> does have a narrow Drude peak followed by a foot. However, the frequency region  $\omega < \omega_L$  has not been fully explored.

For most Fourier-transform spectrometers, the lower limit of the spectrometer range is about  $20\text{--}40 \text{ cm}^{-1}$ . As a result, experiments typically see only the upper frequency part of the shape shown in Fig. 2, containing the characteristic frequency scales  $\omega_H$ , while the part of the spectrum around  $\omega_L$  is usually not reported. This upper frequency part is itself often approximated by a Drude form, which however should not be confused with the true low-frequency behavior of the conductivity. For a number of materials, the experimental reports have hinted toward a cross-over to a low frequency regime which could be Fermi-liquid like. For example, in  $\text{MnSi}$  the resistivity is found to follow  $\rho = AT^2$  in the helimagnetic phase below  $30 \text{ K}$ , while the optical conductivity is given by  $\sigma_1(\omega) \propto \omega^{-0.5}$  down to  $30 \text{ cm}^{-1}$ , even for data taken at  $10 \text{ K}$ , indicating that a cross-over to Fermi-liquid like behavior, if present, would have to occur below  $30 \text{ cm}^{-1}$  (Ref. 40).

This is remedied to a large extent by state of the art time-domain THz spectrometers, which typically span a frequency range from  $1$  up to  $100 \text{ cm}^{-1}$ . The limiting factor in the latter case is provided by diffraction in the long-wavelength limit, imposed by the finite sample size which is typically of the order of a few  $\text{mm}^2$ . In Nb-doped  $\text{SrTiO}_3$ ,  $T^2$  resistivity in a broad temperature range is an indication for Fermi-liquid behavior.<sup>41,42</sup> Time-domain THz data reveal a very narrow zero-frequency mode,<sup>43</sup> similar to that in Fig. 2. On the other hand, whether or not the foot/shoulder at higher frequency is present in the data, has been impossible to establish because strong optical phonons mask the electronic part of the spectrum in the relevant frequency range.

A team involving the present authors recently reported Fermi-liquid like features for underdoped high- $T_c$  cuprates in the pseudo-gap phase, in particular the scaling collapse

of the form  $1/\tau_{\text{opt}}(\omega, T) \propto (\hbar\omega)^2 + (p\pi k_B T)^2$  for a broad range of  $\omega$  and  $T$ .<sup>21</sup> Further analysis of these data in relation to the features discussed in the previous sections is under way.

The examples discussed in this section illustrate the experimental challenges that need to be met in order to establish in a single material the different aspects of the Fermi-liquid optical conductivity, such as displayed in Fig. 2. To the best of our knowledge, this is not available in the literature. Still, with appropriate choice of material, sample geometry and optical instrumentation, those challenges may ultimately be met.

## VI. CONCLUSION

We have derived analytical formula for the universal scaling laws which describe the optical response of local Fermi liquids. These laws depend on two variables,  $\hbar\omega/(2\pi k_B T)$  and  $\omega\tau_{\text{qp}} = \hbar\omega/(2\pi k_B T)(T_0/T)$ , and reveal clear signatures of FL behavior, which are not contained in the simple Drude form. These new laws can help distinguishing, among the ubiquitous deviations from Drude-like behavior, those which prove FL behavior from those which disprove it. We have illustrated this by comparing the scaling forms with DMFT data for the Hubbard model at low doping. Finally, we have reviewed a number of experimental works, and concluded that several of these characteristic features remain to be observed.

## ACKNOWLEDGMENTS

We acknowledge useful discussions with A. Chubukov, M. Dressel, A. J. Leggett, and T. Timusk, and are most grateful to M. Ferrero for discussions and for sharing his codes and his expertise on CT-QMC algorithms and analytical continuation methods. This work was supported by the Swiss National Science Foundation through Division II and MaNEP.

### Appendix A: Kubo formula for a local Fermi liquid

In general, the long-wavelength linear conductivity tensor is related to the current susceptibilities by the Kubo formula

$$\sigma_{\alpha\beta}(\omega) = \frac{ie^2}{\omega} [\chi_{\alpha\beta}(\omega) - \chi_{\alpha\beta}(0)]. \quad (\text{A1})$$

$\chi_{\alpha\beta}(\omega)$  is the retarded macroscopic current-current correlation function, which may be obtained from the analytic continuation of the corresponding imaginary-time function:

$$\chi_{\alpha\beta}(i\Omega_n) = -\frac{1}{L^d} \int_0^{1/k_B T} d\tau e^{i\Omega_n \tau} \langle j_\alpha(\mathbf{q} = 0, \tau) j_\beta(\mathbf{0}, 0) \rangle. \quad (\text{A2})$$

$L$  is the system size,  $d$  the dimensionality,  $j$  is the paramagnetic current operator, and  $\Omega_n = 2n\pi k_B T$  are the

bosonic Matsubara frequencies. The diamagnetic contribution is real and diagonal, and is commonly expressed in terms of the carrier density  $n$  and the carrier mass  $m$ , as  $\chi_{\alpha\beta}(0) = -\delta_{\alpha\beta}(n/m)$ . In interacting Fermi systems, the current susceptibilities can be formally represented by two classes of diagrams. The first class describes the propagation of uncorrelated particle-hole pairs, and can be summed to give the so-called “particle-hole bubble”, formulated in terms of the single-particle spectral function  $A(\mathbf{k}, \varepsilon)$ . The expression of the bubble is

$$\chi_{\alpha\beta}(\omega) = \frac{1}{L^d} \sum_{\mathbf{k}\sigma} v_k^\alpha v_k^\beta \int d\varepsilon_1 d\varepsilon_2 A(\mathbf{k}, \varepsilon_1) A(\mathbf{k}, \varepsilon_2) \times \frac{f(\varepsilon_1) - f(\varepsilon_2)}{\hbar\omega + i0^+ + \varepsilon_1 - \varepsilon_2}. \quad (\text{A3})$$

$f(\varepsilon)$  is the Fermi function, and  $\mathbf{v}_k = (1/\hbar)\nabla E_k$  is the group velocity with  $E_k$  the non-interacting electron dispersion. The second class of diagrams contains all processes involving interactions between the particle and the hole, the so-called “vertex corrections”, which have been shown to vanish by symmetry in local Fermi liquids characterized by a momentum-independent self-energy.<sup>11</sup> This represents a considerable simplification, since the exact current-current correlation function reduces to Eq. (A3). For a local self-energy  $\Sigma(\varepsilon) = \Sigma_1(\varepsilon) + i\Sigma_2(\varepsilon)$ , the spectral function is

$$A(\mathbf{k}, \varepsilon) = \frac{-\Sigma_2(\varepsilon)/\pi}{[\varepsilon - \xi_{\mathbf{k}} - \Sigma_1(\varepsilon)]^2 + [\Sigma_2(\varepsilon)]^2}, \quad (\text{A4})$$

with  $\xi_{\mathbf{k}} = E_{\mathbf{k}} - \mu$ ,  $\mu$  the chemical potential. Inserting Eq. (A4) into Eq. (A3), taking the real part in Eq. (A1), and defining the isotropic conductivity as an average over the spatial coordinates,  $\sigma(\omega) \equiv (1/d) \sum_{\alpha=1}^d \sigma_{\alpha\alpha}(\omega)$ , directly leads to Eqs. (8).

We note in passing that Eqs. (8) provide an interesting generalization of the Drude formula for the dc conductivity:  $\sigma_1(0)$  can be transformed into

$$\sigma_1(0) = \int d\varepsilon [-f'(\varepsilon)] \frac{\hbar}{2|\Sigma_2(\varepsilon)|} \times \int du \Phi(\varepsilon - \Sigma_1(\varepsilon) - u|\Sigma_2(\varepsilon)|) \frac{2/\pi}{(u^2 + 1)^2}, \quad (\text{A5})$$

with  $f'$  the derivative of the Fermi function. Since  $\Phi$  generally is a slow function of its argument, we may expand about  $u = 0$ , and get at lowest order:

$$\sigma_1(0) \approx \int d\varepsilon [-f'(\varepsilon)] \frac{\hbar}{2|\Sigma_2(\varepsilon)|} \Phi(\varepsilon - \Sigma_1(\varepsilon)). \quad (\text{A6})$$

If  $\Phi$  is taken constant, we recover the well-known fact that the dc conductivity does not depend on the real part of the self-energy, explaining the absence of dynamical effective mass renormalization in the Drude formula. A weak dependence on the dynamical effective mass only enters through the energy dependence of the function  $\Phi(\xi)$ .

The function  $\Phi(\xi)$  in Eq. (8b) is generally a slowly-varying function of its argument. After replacing  $\Phi(\xi)$  by  $\Phi(0)$  in Eq. (8a), the  $\xi$  integration can be performed by means of the identity

$$\frac{1}{\pi} \int d\xi \frac{\Gamma_1 \Gamma_2}{[(\varepsilon_1 - \xi)^2 + \Gamma_1^2][(\varepsilon_2 - \xi)^2 + \Gamma_2^2]} = \frac{\Gamma_1 + \Gamma_2}{(\varepsilon_1 - \varepsilon_2)^2 + (\Gamma_1 + \Gamma_2)^2}, \quad (\text{A7})$$

leading to

$$\sigma_1(\omega) = \frac{\Phi(0)}{\omega} \int d\varepsilon [f(\varepsilon) - f(\varepsilon + \hbar\omega)] \times \frac{-\Sigma_2(\varepsilon) - \Sigma_2(\varepsilon + \hbar\omega)}{[\hbar\omega + \Sigma_1(\varepsilon) - \Sigma_1(\varepsilon + \hbar\omega)]^2 + [\Sigma_2(\varepsilon) + \Sigma_2(\varepsilon + \hbar\omega)]^2}. \quad (\text{A8})$$

Equivalently, this can be rewritten as:

$$\sigma_1(\omega) = \frac{\Phi(0)}{\omega} \int d\varepsilon [f(\varepsilon) - f(\varepsilon + \hbar\omega)] \times \text{Re} \left[ \frac{i}{\hbar\omega + \Sigma^*(\varepsilon) - \Sigma(\varepsilon + \hbar\omega)} \right]. \quad (\text{A9})$$

Finally, the requirements that the imaginary part of the conductivity is positive for positive  $\omega$ , and analytic for  $\text{Im } \omega > 0$ , lead to Eq. (9). It can also be seen that the correction to Eq. (9), due to the first-order variation of  $\Phi(\xi)$ , vanishes identically if the self-energy has the symmetry property  $\Sigma(-\varepsilon) = -\Sigma^*(\varepsilon)$ , as it is the case for the model Eq. (11).

## Appendix B: Calculation of the $\mathcal{S}$ function

In order to evaluate the  $\mathcal{S}$  function, we use the exact representation

$$\frac{1}{e^{\pi(u-x)} + 1} - \frac{1}{e^{\pi(u+x)} + 1} = \frac{1}{\pi} \sum_{n=-\infty}^{+\infty} \left( \frac{1}{ip_n + x - u} - \frac{1}{ip_n - x - u} \right) \quad (\text{B1})$$

with  $p_n = 2n + 1$ . Changing variable in the integral in (13), we see that each term with  $p_n < 0$  is equal to the corresponding term with  $p_{-n-1} = -p_n > 0$ , so that the sum can be rewritten as a sum on  $n \geq 0$ . The integrations are elementary,

$$\begin{aligned} & \frac{1}{\pi} \int du \left( \frac{1}{ip_n + x - u} - \frac{1}{ip_n - x - u} \right) \frac{1}{1 + x^2 - iy + u^2} \\ &= \frac{i}{r(x, y)} \left( \frac{1}{p_n + r(x, y) + ix} - \frac{1}{p_n + r(x, y) - ix} \right) \\ & r(x, y) = \sqrt{1 + x^2 - iy}, \end{aligned} \quad (\text{B2})$$

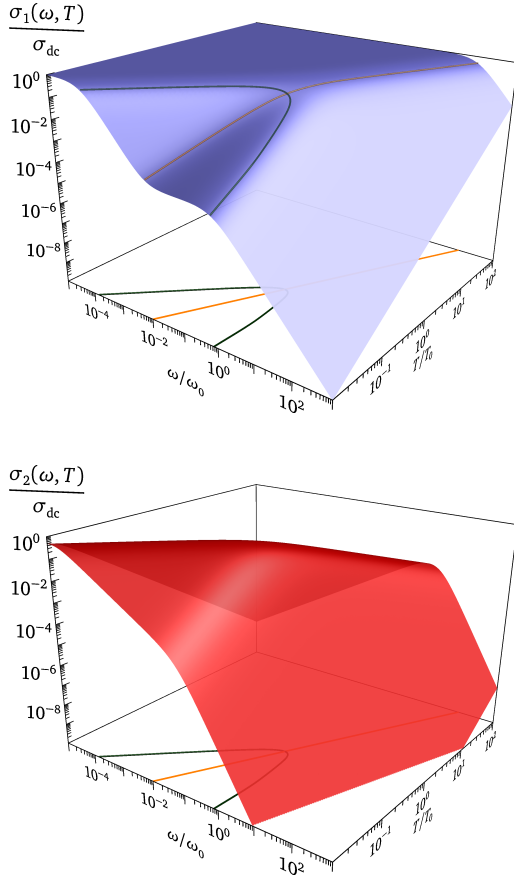


FIG. 13. Real part (top) and imaginary part (bottom) of the optical conductivity normalized by the dc value, as a function of frequency and temperature.  $T_0$  is defined in Eq. (11), and  $\omega_0 = 2\pi k_B T_0/\hbar$ . The straight orange lines indicate  $\hbar\omega = 2\pi k_B T$ , and the green lines corresponds to the dome in Fig. 3.

and we may recast the sums in terms of the digamma function  $\psi(z) = \lim_{M \rightarrow \infty} [\log M - \sum_{n=0}^M 1/(n+z)]$ , to finally get Eq. (13c).

Equation (14) shows that the conductivity normalized to the dc value is given by  $\mathcal{S} \left( \frac{\omega/\omega_0}{T/T_0}, \frac{\omega/\omega_0}{(T/T_0)^2} \right)$ . This is displayed as a function of frequency and temperature in Fig. 13. The function  $\mathcal{S}$  is well approximated by the simple form  $\mathcal{S}(x, y) \approx 1/(1 + x^2 - 3iy/4)$  over the whole  $(x, y)$  plane.

### Appendix C: Comparing Fermi-liquid and Drude formula

In the Drude regime, defined by  $\hbar\omega \ll 2\pi k_B T$  and  $\omega\tau_{qp} \sim 1$ , the conductivity of a Fermi liquid is a universal function of  $\omega\tau_{qp}$  given by Eq. (15). This function is displayed in Fig. 14. The imaginary part  $\sigma_2$  increases first linearly with a slope  $1/2 + 3\zeta(3)/\pi^2 \approx 0.865$ , reaches a maximum at  $\omega\tau_{qp} \approx 1.162$ , and then decreases as  $12/\pi^2(\omega\tau_{qp})^{-1}$ . The real part decreases as  $16/\pi^2(\omega\tau_{qp})^{-2}$ , and crosses the imaginary part at  $\omega\tau_{qp} \approx 1.198$ , slightly above the point where  $\sigma_2$  has its maximum. In the Drude

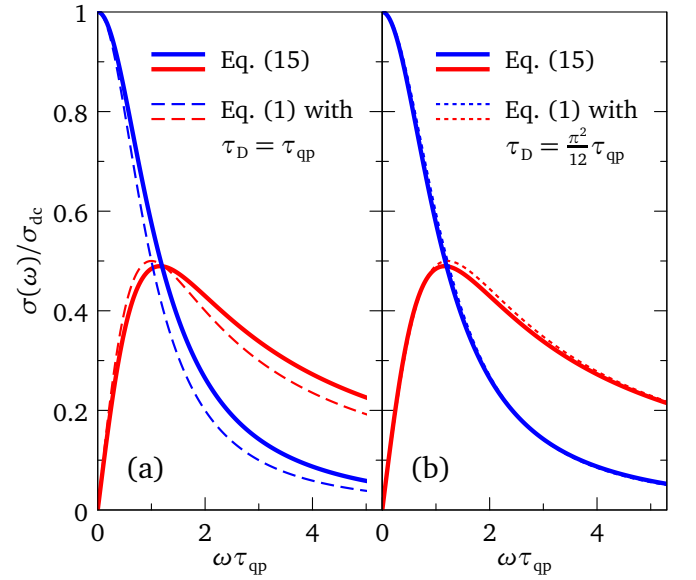


FIG. 14. Comparison of the Fermi-liquid conductivity in the Drude regime, Eq. (15), with the Drude model, Eq. (1). The solid blue and red lines show the real and imaginary parts of Eq. (15), respectively. The dashed lines in (a) show the Drude model assuming  $\tau_D = \tau_{qp}$ . The dotted lines in (b) show the Drude model assuming  $\tau_D = (\pi^2/12)\tau_{qp}$  (see text).

model Eq. (1),  $\sigma_2$  increases first like  $\omega\tau_D$ , reaches a maximum at  $\omega\tau_D = 1$ , and then decreases as  $(\omega\tau_{qp})^{-1}$ ;  $\sigma_1$  decreases as  $(\omega\tau_D)^{-2}$ , and crosses  $\sigma_2$  at its maximum.

When approximating the low-frequency response of a Fermi liquid by the Drude model, it is not possible to choose the time  $\tau_D$  such that the four remarkable features—initial slope and maximum of  $\sigma_2$ , asymptotic decay of  $\sigma_1$  and  $\sigma_2$ —are all described exactly. If one takes  $\tau_D = \tau_{qp}$ , none of these features is correctly reproduced, as illustrated in Fig. 14a. Matching the initial slope of  $\sigma_2$  in both models implies  $\tau_D = 0.865\tau_{qp}$ , matching the maximum of  $\sigma_2$  means  $\tau_D = \tau_{qp}/1.162$ , matching the asymptotic decays of  $\sigma_1$  and  $\sigma_2$  leads respectively to  $\tau_D = (\pi/4)\tau_{qp}$  and  $\tau_D = (\pi^2/12)\tau_{qp}$ . All four determinations of  $\tau_D/\tau_{qp}$  are close to 0.8. The choice  $\tau_D = (\pi^2/12)\tau_{qp}$ , because it gives the correct asymptotic decay of  $\sigma_2$ , also ensures that the spectral weight is the same in both models by the Kramers-Kronig relations. It is furthermore the closest to the average of the four determinations. Figure 14b shows a comparison of the Fermi-liquid model with the Drude model, assuming  $\tau_D = (\pi^2/12)\tau_{qp}$ .

### Appendix D: Memory function in the thermal and Drude regimes

By solving Eq. (2) for  $M(\omega)$ , identifying  $\sigma(\omega)$  with the Fermi-liquid result Eqs. (13), and expanding for large  $y = \omega\tau_{qp}$  with the help of Eq. (17), one arrives at the expression (21) for the memory function in the thermal

regime. Inserting (21) back into Eq. (2), one recovers the generalized Drude form Eqs. (18) and (19). From an experimental perspective, one sees in (21) that a plot of  $\omega M_2(\omega)/[\omega + M_1(\omega)]$  in the region  $\hbar\omega \sim 2\pi k_B T$  should allow to determine the parameter  $T_0$ .

We note that, while the real part of  $M$  depends on the total spectral weight  $\epsilon_0\omega_p^2$ , the normalized imaginary part  $M_2(\omega)/M_2(0)$  does not, since  $M_2(\omega)/M_2(0) = \text{Re} \sigma_{\text{dc}}/\sigma(\omega)$  as shown e.g. in Eq. (7). Unlike  $M_1(\omega)$ ,  $M_2(\omega)/M_2(0)$  can therefore be determined accurately using a low-energy model. With the Fermi-liquid model (13), we have

$$\frac{M_2(\omega)}{M_2(0)} = \text{Re} \frac{1}{\mathcal{S}(x, y)}. \quad (\text{D1})$$

As  $\lim_{y \rightarrow \infty} \text{Re}[1/\mathcal{S}(x, y)] = (\pi/3)^2(1+x^2)$ , one sees that the scaling function for  $M_2(\omega)$  in the thermal regime extrapolates to the value  $(\pi/3)^2 M_2(0)$  at  $\omega = 0$ , as can be seen in Fig. 5.

The behavior of  $M_2(\omega)/M_2(0)$  in the Drude regime  $\omega\tau_{\text{qp}} < 1$  is quadratic and given by

$$\frac{M_2(\omega)}{M_2(0)} = 1 + (\omega\tau_{\text{qp}})^2 \left[ a + b \left( \frac{T}{T_0} \right)^2 \right], \quad (\text{D2})$$

where  $a$  and  $b$  are the numerical constants  $a = 1/8 + \pi^2/80 - 3\zeta(3)/(4\pi^2) - (3\zeta(3)/\pi^2)^2 \approx 0.0235$  and  $b = 1/2 + \pi^2/60 + 3\zeta(3)/\pi^2 \approx 1.03$ . This is plotted in Fig. 5a as the thin line.

#### Appendix E: Impurity scattering, robustness of the $2\pi$ factor

In this appendix, we show that the inclusion of a constant scattering rate  $-i\Gamma$  in the Fermi-liquid self-energy Eq. (11) does not change the scaling of the optical conductivity in the thermal regime. A frequency-independent scattering rate can crudely describe the effect of impurity scattering. On adding  $-i\Gamma$  to the self-energy, the only change induced in Eqs. (13) occurs in the expression of the function  $\mathcal{S}$ :

in the denominator of the integrand, 1 is replaced by  $1 + 2Z\tau_{\text{qp}}\Gamma/\hbar$ . The correction term  $\sim \Gamma/T^2$  is the ratio between the impurity and the electron-electron scattering rates. This change can be absorbed into a redefinition of the variable  $y$ :

$$y = \frac{\bar{\omega}}{\bar{T}^2} \rightarrow y_1 + iy_2 = \frac{\bar{\omega} + iZ\Gamma/(\pi k_B T_0)}{\bar{T}^2}. \quad (\text{E1})$$

The same modification made in the analytical form Eq. (13c) yields the scaling function in the presence of impurity scattering. It should be noted that, with this modification, the function  $\mathcal{S}$  is not unity in the dc limit, and therefore the dc conductivity is different from  $\sigma_{\text{dc}}$  as defined in Eq. (13). In particular, the residual dc resistivity can be evaluated as  $\rho_0 = 2\Gamma/[\hbar\Phi(0)]$ .

If  $\omega \gg 2Z\Gamma/\hbar$ , we can expand in the thermal regime like in Eq. (17), which must then be replaced by

$$\mathcal{S}(x, y_1 \rightarrow \infty, y_2) = \frac{12i}{\pi^2 y_1} + \frac{16}{\pi^2 y_1^2} \left( 1 + x^2 + \frac{3}{4} y_2 \right). \quad (\text{E2})$$

Consequently, we find that the optical scattering rate reflects the increased quasiparticle scattering rate (with an extra factor of two), but that the frequency/temperature scaling is unchanged:

$$\frac{\hbar}{\tau_{\text{opt}}(\omega)} = \frac{2}{3\pi k_B T_0} \left[ (\hbar\omega)^2 + (2\pi k_B T)^2 \right] + 2Z\Gamma. \quad (\text{E3})$$

The impurity scattering, however, reduces the frequency/temperature domain below the dome in Fig. 3, where  $\tau_{\text{opt}}(\omega) > 1/\omega$ . The equation of the dome in the presence of impurity scattering is

$$T_1(\omega) = T_0 \sqrt{\frac{3}{4} \left( \bar{\omega} - \frac{Z\Gamma}{\pi k_B T_0} \right) - \bar{\omega}^2}. \quad (\text{E4})$$

Hence the dome disappears—and consequently the shoulder in the log-log plot of  $\sigma_1(\omega)$ —if  $Z\Gamma > 3\pi k_B T_0/16$ .

<sup>1</sup> P. Drude, *Ann. Phys.* **306**, 566 (1900).

<sup>2</sup> M. Dressel and M. Scheffler, *Ann. Phys. (Leipzig)* **15**, 535 (2006).

<sup>3</sup> L. Landau, *Zh. Eksp. Teor. Fiz.* **30**, 1058 (1956) [*Sov. Phys. JETP* **3**, 920 (1957)].

<sup>4</sup> A. V. Chubukov and D. L. Maslov, *Phys. Rev. B* **86**, 155136 (2012).

<sup>5</sup> D. L. Maslov and A. V. Chubukov, *Phys. Rev. B* **86**, 155137 (2012).

<sup>6</sup> M. C. Nuss and J. Orenstein, in *Millimeter and Submillimeter Spectroscopy of Solids*, Topics in Applied Physics, Vol. 74, edited by G. Grüner (Springer, New York, 1998) pp. 7–50.

<sup>7</sup> S. L. Dexheimer, ed., *Terahertz Spectroscopy: Principles and Applications* (CRC Press, Boca Raton, 2007).

<sup>8</sup> D. N. Basov, R. D. Averitt, D. van der Marel, M. Dressel, and K. Haule, *Rev. Mod. Phys.* **83**, 471 (2011).

<sup>9</sup> W. Götze and P. Wölfle, *Phys. Rev. B* **6**, 1226 (1972).

<sup>10</sup> A. Georges and G. Kotliar, *Phys. Rev. B* **45**, 6479 (1992).

<sup>11</sup> A. Khurana, *Phys. Rev. Lett.* **64**, 1990 (1990).

<sup>12</sup> W. Lee, D. Rainer, and W. Zimmermann, *Physica C* **159**, 535 (1989).

<sup>13</sup> S. V. Shulga, O. V. Dolgov, and E. G. Maksimov, *Physica C* **178**, 266 (1991).

<sup>14</sup> P. B. Allen, *arXiv:cond-mat/0407777* (2004).

<sup>15</sup> One sees this from Eq. (18):  $\sigma_2 \sim 1/[\omega + \tau_{\text{opt}}^{-2}(\omega)/\omega]$ . Hence the  $1/\omega^3$  results from the  $\omega^2$  of the optical scattering rate. At frequencies well above  $\omega_{\pm}$  (defined in Sec. IV),  $\tau_{\text{opt}}^{-1}$  is expected to saturate to a frequency-independent value, so that the correct

- asymptotic  $1/\omega$  decay of  $\sigma_2$  is recovered. The saturation of  $\tau_{\text{opt}}^{-1}$  does not affect the power law of  $\sigma_1$ , since it can be seen to go like  $1/[\omega^2\tau_{\text{opt}}(\omega) + \tau_{\text{opt}}^{-1}(\omega)]$ .
- <sup>16</sup> See R. N. Gurzhi, Sov. Phys. JETP **35**(8), 673 (1959), and references therein.
  - <sup>17</sup> P. E. Sulewski, A. J. Sievers, M. B. Maple, M. S. Torikachvili, J. L. Smith, and Z. Fisk, *Phys. Rev. B* **38**, 5338 (1988).
  - <sup>18</sup> T. Katsufuji and Y. Tokura, *Phys. Rev. B* **60**, 7673 (1999).
  - <sup>19</sup> J. Yang, J. Hwang, T. Timusk, A. S. Sefat, and J. E. Greedan, *Phys. Rev. B* **73**, 195125 (2006).
  - <sup>20</sup> M. Dressel, *J. Phys.: Cond. Mat.* **23**, 293201 (2011).
  - <sup>21</sup> S. I. Mirzaei, D. Stricker, J. N. Hancock, C. Berthod, A. Georges, E. van Heumen, M. K. Chan, X. Zhao, Y. Li, M. Greven, N. Barišić, and D. van der Marel, [arXiv:1207.6704](https://arxiv.org/abs/1207.6704) (2012).
  - <sup>22</sup> U. Nagel, T. Uleksin, T. Rööf, R. P. S. M. Lobo, P. Lejay, C. C. Homes, J. S. Hall, A. W. Kinross, S. K. Purdy, T. Munsie, T. J. Williams, G. M. Luke, and T. Timusk, *Proc. Natl. Acad. Sci. USA* **109**, 19161 (2012).
  - <sup>23</sup> A. Georges, G. Kotliar, W. Krauth, and M. J. Rozenberg, *Rev. Mod. Phys.* **68**, 13 (1996).
  - <sup>24</sup> M. Jarrell, J. K. Freericks, and T. Pruschke, *Phys. Rev. B* **51**, 11704 (1995).
  - <sup>25</sup> J. Merino, M. Dumm, N. Drichko, M. Dressel, and R. H. McKenzie, *Phys. Rev. Lett.* **100**, 086404 (2008).
  - <sup>26</sup> E. Gull, A. J. Millis, A. I. Lichtenstein, A. N. Rubtsov, M. Troyer, and P. Werner, *Rev. Mod. Phys.* **83**, 349 (2011).
  - <sup>27</sup> M. Ferrero and O. Parcollet, “TRIQS: a Toolbox for Research on Interacting Quantum Systems” .
  - <sup>28</sup> R. Bulla, T. A. Costi, and T. Pruschke, *Rev. Mod. Phys.* **80**, 395 (2008).
  - <sup>29</sup> R. Žitko, “NRG Ljubljana – open source numerical renormalization group code” .
  - <sup>30</sup> X. Deng, J. Mravlje, R. Žitko, M. Ferrero, G. Kotliar, and A. Georges, [arXiv:1210.1769](https://arxiv.org/abs/1210.1769) (2012).
  - <sup>31</sup> B. C. Webb, A. J. Sievers, and T. Mihalisin, *Phys. Rev. Lett.* **57**, 1951 (1986).
  - <sup>32</sup> A. M. Awasthi, W. P. Beyermann, J. P. Carini, and G. Grüner, *Phys. Rev. B* **39**, 2377 (1989).
  - <sup>33</sup> L. Degiorgi, *Rev. Mod. Phys.* **71**, 687 (1999).
  - <sup>34</sup> C. Geibel, C. Schank, S. Thies, H. Kitazawa, C. D. Bredl, A. Böhm, M. Rau, A. Grauel, R. Caspary, R. Helfrich, U. Ahlheim, G. Weber, and F. Steglich, *Z. Phys. B Cond. Mat.* **84**, 1 (1991).
  - <sup>35</sup> A. Krimmel, P. Fischer, B. Roessli, H. Maletta, C. Geibel, C. Schank, A. Grauel, A. Loidl, and F. Steglich, *Z. Phys. B Cond. Mat.* **86**, 161 (1992).
  - <sup>36</sup> K. Ghosh, S. Ramakrishnan, and G. Chandra, *Phys. Rev. B* **47**, 8305 (1993).
  - <sup>37</sup> F. Wastin, E. Bednarczyk, and J. Rebizant, *J. All. Comp.* **271**, 437 (1998).
  - <sup>38</sup> M. Scheffler, M. Dressel, M. Jourdan, and H. Adrian, *Nature (London)* **438**, 1135 (2005).
  - <sup>39</sup> M. Dumm, D. Faltermeier, N. Drichko, M. Dressel, C. Mézière, and P. Batail, *Phys. Rev. B* **79**, 195106 (2009).
  - <sup>40</sup> F. P. Mena, D. van der Marel, A. Damascelli, M. Fäth, A. A. Menovsky, and J. A. Mydosh, *Phys. Rev. B* **67**, 241101(R) (2003).
  - <sup>41</sup> S. N. Klimin, J. Tempere, D. van der Marel, and J. T. Devreese, *Phys. Rev. B* **86**, 045113 (2012).
  - <sup>42</sup> D. van der Marel, J. L. M. van Mechelen, and I. I. Mazin, *Phys. Rev. B* **84**, 205111 (2011).
  - <sup>43</sup> J. L. M. van Mechelen, D. van der Marel, C. Grimaldi, A. B. Kuzmenko, N. P. Armitage, N. Reyren, H. Hagemann, and I. I. Mazin, *Phys. Rev. Lett.* **100**, 226403 (2008).